

NASA TECH BRIEF



NASA Tech Briefs announce new technology derived from the U.S. space program. They are issued to encourage commercial application. Tech Briefs are available on a subscription basis from the National Technical Information Service, Springfield, Virginia 22151. Requests for individual copies or questions relating to the Tech Brief program may be directed to the Technology Utilization Division, NASA, Code UT, Washington, D.C. 20546.

Thermal Tuning of Organic Dye Lasers

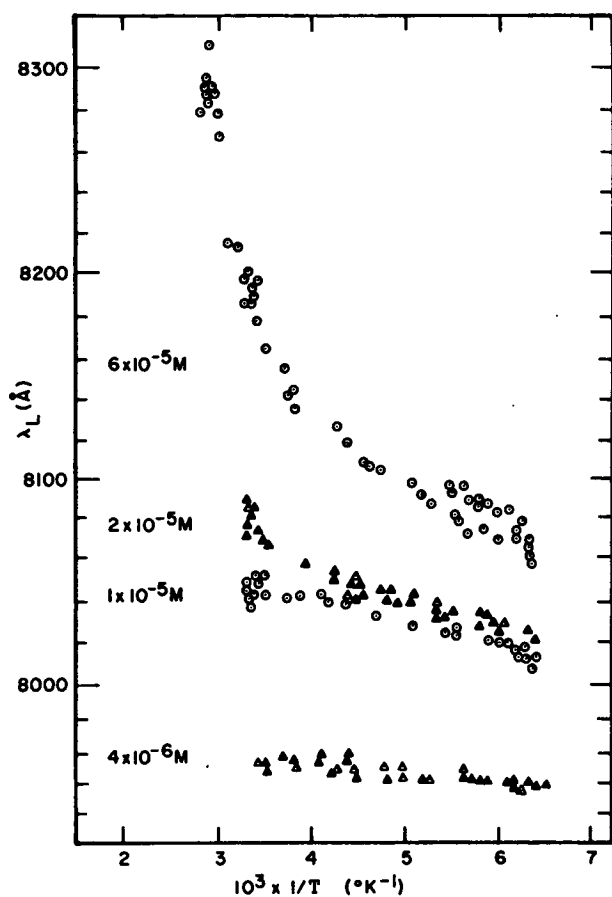


Figure 1. Center Lasing Frequency as a Function of Temperature for Four Dye Concentrations

A new, non-mechanical method for tuning liquid laser wavelengths replaces previous mechanical procedures such as varying the cavity Q or the nature or concentration of the lasing medium. The new

method electrically varies the temperature of the lasing medium.

The wavelength spectrum of an organic-dye laser (3,3'-diethylthiatricarbocyanine at various concentrations in ethanol), contained in a liquid nitrogen cooled dewar and longitudinally pumped by a Q -switched ruby laser, was measured as a function

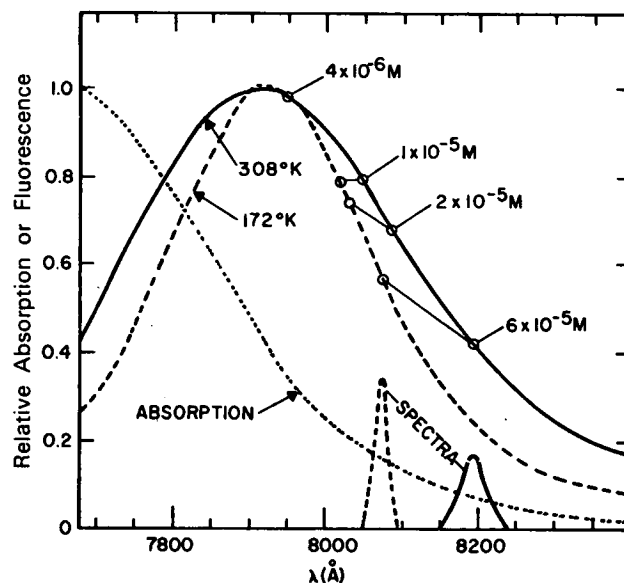


Figure 2. Measured Absorption and Fluorescence Spectra. The circles indicate lasing wavelengths at different concentrations. Below two such points are shown typical spectra recorded for a $6 \times 10^{-6} M$ solution and plotted on an identical intensity scale for the temperatures 172° and $308^\circ K$.

of temperature between -117° and $78^\circ C$ (Fig. 1). The results were in qualitative agreement with the model of a vibrationally broadened two-level system, each level being separately thermalized. The absorp-

(continued overleaf)

tion and fluorescence spectra appear in Figure 2.

The conversion efficiency (the ratio of output power to pump power) of this dye laser can be increased by lowering the temperature. For example, an increase by a factor of 3 can be produced by a temperature change of from $+20^{\circ}$ to -60°C .

The method may be used for investigating the behavior of laser dyes, and may lead to a broad, tunable, light source for spectroscopic applications, especially for measurements of long-path absorption.

Note:

Requests for further information may be directed to:

Technology Utilization Officer
Headquarters
National Aeronautics
and Space Administration
Washington, DC. 20546
Reference: TSP70-10480

Patent status:

This invention is owned by NASA, and a patent application has been filed. Royalty-free, nonexclusive licenses for its commercial use will be granted by NASA. Inquiries concerning license rights should be made to:

Patent Counsel
Mail Code 200-11A
Ames Research Center
Moffett Field, California 94035

Source: G. T. Schappert, K. W. Billman,
and D. C. Burnham
Electronics Research Center
(ERC-10187)